SCIENTIFIC OPINION



Safety assessment of the process Reciclar, based on the EREMA Basic technology, used to recycle post-consumer PET into food contact materials

EFSA Panel on Food Contact Materials, Enzymes and Processing Aids (CEP) | Claude Lambré | José Manuel Barat Baviera | Claudia Bolognesi | Andrew Chesson | Pier Sandro Cocconcelli | Riccardo Crebelli | David Michael Gott | Konrad Grob | Marcel Mengelers | Alicja Mortensen | Gilles Rivière | Inger-Lise Steffensen | Christina Tlustos | Henk Van Loveren | Laurence Vernis | Holger Zorn | Vincent Dudler | Maria Rosaria Milana | Constantine Papaspyrides | Maria de Fátima Tavares Poças | Alexandros Lioupis | Marta Lopez Villegas | Evgenia Lampi

Correspondence: fip@efsa.europa.eu

Abstract

The EFSA Panel on Food Contact Materials, Enzymes and Processing Aids (CEP) assessed the safety of the recycling process Reciclar (EU register number RECYC314), which uses the EREMA Basic technology. The input material is and dried poly(ethylene terephthalate) (PET) flakes originating from collected post-consumer PET containers, including no more than 5% PET from non-food consumer applications. The flakes are heated in a continuous reactor under vacuum before being extruded. Having examined the challenge test provided, the Panel concluded that the continuous decontamination (step 2), for which a challenge test was provided, is critical in determining the decontamination efficiency of the process. The operating parameters to control the performance of this step are temperature, pressure and residence time. It was demonstrated that this recycling process is able to ensure a level of migration of potential unknown contaminants into food below the conservatively modelled migration of 0.1 μg/kg food, derived from the exposure scenario for infants, when such recycled PET is used at up to 100% in mixtures with virgin PET. Therefore, the Panel concluded that the recycled PET obtained from this process is not of safety concern when used at up to 100% in mixtures with virgin PET for manufacturing of materials and articles for contact with all types of foodstuffs, including drinking water bottles, except drinking water, for long-term storage at room temperature or below, with or without hotfill. Articles made of this recycled PET are not intended to be used in microwave or conventional ovens and such uses are not covered by this evaluation.

KEYWORDS

EREMA Basic, food contact materials, plastic, poly(ethylene terephthalate) (PET), Reciclar S.A., recycling process, safety assessment

This is an open access article under the terms of the Creative Commons Attribution-NoDerivs License, which permits use and distribution in any medium, provided the original work is properly cited and no modifications or adaptations are made.

© 2024 European Food Safety Authority. EFSA Journal published by Wiley-VCH GmbH on behalf of European Food Safety Authority.

Abs	Abstract1						
1.	. Introduction						
	1.1.	Background and Terms of Reference as provided by the requestor	3				
	1.2.	Terms of Reference	3				
	1.3.	Interpretation of the Terms of Reference	3				
2.	·						
	2.1.	Data	3				
	2.2.	Methodologies	4				
3.	Asse	ssment	4				
	3.1.	General information	4				
	3.2.	Description of the process					
		3.2.1. General description					
		3.2.2. Characterisation of the input					
	3.3.	EREMA Basic technology					
		3.3.1. Description of the main steps					
		3.3.2. Decontamination efficiency of the recycling process					
	3.4.	Discussion					
4.	Conc	lusions					
5.		Recommendation					
6.	Recommendation						
Abk		tions					
		f interest					
		r					
	•	number					
		t for non-EFSA content					
		mbers					
		ice					
_		25					
		< A					
		(B					
Apr	pendix	(C	13				

1 | INTRODUCTION

1.1 Background and Terms of Reference as provided by the requestor

Recycled plastic materials and articles shall only be placed on the market if the recycled plastic is from an authorised recycling process. Before a recycling process is authorised, the European Food Safety Authority (EFSA)'s opinion on its safety is required. This procedure has been established in Article 5 of Regulation (EC) No 282/2008^{1,2} on recycled plastic materials intended to come into contact with foods and Articles 8 and 9 of Regulation (EC) No 1935/2004³ on materials and articles intended to come into contact with food.

According to this procedure, the industry submits applications to the competent authorities of Member States, which transmit the applications to EFSA for evaluation.

In this case, EFSA received from the German competent authority (Federal Office of Consumer Protection and Food Safety), an application for evaluation of the recycling process Reciclar, European Union (EU) register No RECYC314. The request has been registered in EFSA's register of received questions under the number EFSA-Q-2022-00286. The dossier was submitted on behalf of Reciclar S.A., Heredia 3220, Sarandí Buenos Aires Argentina, CP 1872, Argentina (see 'Documentation provided to EFSA').

1.2 Terms of Reference

The German competent authority (Federal Office of Consumer Protection and Food Safety) requested the safety evaluation of the recycling process Reciclar, in accordance with Article 5 of Regulation (EC) No 282/2008.

1.3 Interpretation of the Terms of Reference

According to Article 5 of Regulation (EC) No 282/2008 on recycled plastic materials intended to come into contact with foods, EFSA is required to carry out risk assessments on the risks originating from the migration of substances from recycled food contact plastic materials and articles into food and deliver a scientific opinion on the recycling process examined.

According to Article 4 of Regulation (EC) No 282/2008, EFSA will evaluate whether it has been demonstrated in a challenge test, or by other appropriate scientific evidence, that the recycling process is able to reduce the contamination of the plastic input to a concentration that does not pose a risk to human health. The poly(ethylene terephthalate) (PET) materials and articles used as input of the process as well as the conditions of use of the recycled PET are part of this evaluation.

2 | DATA AND METHODOLOGIES

2.1 | Data

The applicant has submitted a dossier following the 'EFSA guidelines for the submission of an application for the safety evaluation of a recycling process to produce recycled plastics intended to be used for the manufacture of materials and articles in contact with food, prior to its authorisation' (EFSA, 2008) and the 'Administrative guidance for the preparation of applications on recycling processes to produce recycled plastics intended to be used for manufacture of materials and articles in contact with food' (EFSA, 2021). In accordance with Art. 38 of the Commission Regulation (EC) No 178/2002⁴ and taking into account the protection of confidential information and of personal data in accordance with Articles 39 to 39e of the same Regulation and of the Decision of the EFSA's Executive Director laying down practical arrangements concerning transparency and confidentiality, ⁵ the non-confidential version of the dossier is published on Open.EFSA. ⁶

According to Art. 32c(2) of Regulation (EC) No 178/2002 and to the Decision of EFSA's Executive Director laying down the practical arrangements on pre-submission phase and public consultations, EFSA carried out a public consultation on the non-confidential version of the application from 13 September 2023 to 04 October 2023, for which no comments were received.

¹Commission Regulation (EC) No 282/2008 of 27 March 2008 on recycled plastic materials and articles intended to come into contact with foods and amending Regulation (EC) No 2023/2006. OJ L 86, 28.3.2008, pp. 9–18.

²Commission Regulation (EC) No 282/2008 was repealed by Commission Regulation (EU) 2022/1616 of 15 September 2022 on recycled plastic materials and articles intended to come into contact with foods, and repealing Regulation (EC) No 282/2008 (OJ L 243 20.9.2022, p. 3) which entered into force on 10 October 2022. Applications submitted to EU Member State competent authorities before the date of entry into force of Commission Regulation (EU) 2022/1616 are evaluated by EFSA in accordance with Commission Regulation (EC) No 282/2008.

³Regulation (EC) No 1935/2004 of the European parliament and of the council of 27 October 2004 on materials and articles intended to come into contact with food and repealing Directives 80/590/EEC and 89/109/EEC. OJ L 338, 13.11.2004, pp. 4–17.

⁴Commission Regulation (EC) No 178/2002 of the European Parliament and of the Council of 28 January 2002 laying down the general principles and requirements of food law, establishing the European Food Safety Authority and laying down procedures in matters of food safety. OJ L 31, 1.2.2002, pp. 1–48.

 $[\]label{prop:special} {}^{5} \text{Decision available at https://www.efsa.europa.eu/en/corporate-pubs/transparency-regulation-practical-arrangements}.$

⁶The non-confidential version of the dossier, following EFSA's assessment of the applicant's confidentiality requests, is published on Open.EFSA and is available at the following link: https://open.efsa.europa.eu/dossier/FCM-2022-5612.

⁷Decision available at: https://www.efsa.europa.eu/sites/default/files/corporate_publications/files/210111-PAs-pre-submission-phase-and-public-consultations.pdf.

Additional information was provided by the applicant during the assessment process in response to requests from EFSA sent on 23 February 2023, 19 September 2023 and 15 November 2023 (see 'Documentation provided to EFSA').

The following information on the recycling process was provided by the applicant and used for the evaluation:

- General information:
 - general description,
 - existing authorisations.
- Specific information:
 - recycling process,
 - characterisation of the input,
 - determination of the decontamination efficiency of the recycling process,
 - characterisation of the recycled plastic,
 - intended application in contact with food,
 - compliance with the relevant provisions on food contact materials and articles,
 - process analysis and evaluation,
 - operating parameters.

2.2 | Methodologies

The risks associated with the use of recycled plastic materials and articles in contact with food come from the possible migration of chemicals into the food in amounts that would endanger human health. The quality of the input, the efficiency of the recycling process to remove contaminants as well as the intended use of the recycled plastic are crucial points for the risk assessment (EFSA, 2008).

The criteria for the safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for the manufacture of materials and articles in contact with food are described in the scientific opinion developed by the EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids (EFSA CEF Panel, 2011). The principle of the evaluation is to apply the decontamination efficiency of a recycling technology or process, obtained from a challenge test with surrogate contaminants, to a reference contamination level for post-consumer PET, conservatively set at 3 mg/kg PET for contaminants resulting from possible misuse. The resulting residual concentration of each surrogate contaminant in recycled PET ($C_{\rm res}$) is compared with a modelled concentration of the surrogate contaminants in PET ($C_{\rm mod}$). This $C_{\rm mod}$ is calculated using generally recognised conservative migration models so that the related migration does not give rise to a dietary exposure exceeding 0.0025 µg/kg body weight (bw) per day (i.e. the human exposure threshold value for chemicals with structural alerts for genotoxicity), below which the risk to human health would be negligible. If the $C_{\rm res}$ is not higher than the $C_{\rm mod}$, the recycled PET manufactured by such recycling process is not considered to be of safety concern for the defined conditions of use (EFSA CEF Panel, 2011).

The assessment was conducted in line with the principles described in the EFSA Guidance on transparency in the scientific aspects of risk assessment (EFSA, 2009) and considering the relevant guidance from the EFSA Scientific Committee.

3 | ASSESSMENT

3.1 | General information⁸

According to the applicant, the recycling process Reciclar is intended to recycle food grade PET containers using the EREMA Basic technology. The recycled PET is intended to be used at up to 100% for bottles for mineral water, soft drinks, juices and beer as well as for thermoformed trays/containers, e.g. for fruits, vegetables, cooked and uncooked meats, dairy products and desserts, for long-term food storage at room temperature or below, with or without hotfill. The final articles are not intended to be used in microwave or conventional ovens.

3.2 Description of the process

3.2.1 | General description⁹

The recycling process Reciclar produces recycled PET pellets from PET containers from post-consumer collection systems (kerbside and deposit systems).

⁸Technical dossier, section 'Recycling process'.

⁹Technical dossier, sections 'Recycling process', 'Characterisation of the input' and 'Characterisation of the recycled plastic'.

8314732, 2024, 1, Downloaded from https://efsa.onlinelibrary.wiley.com/doi/10.2903/j.efsa.2024.8518 by Cochrane Argentina, Wiley Online Library on [31/10/2024]. See the Terms and Conditions (https://onlinelibrary.wiley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA

articles are governed by the applicable Creative Commons License

It comprises the three steps below.

<u>Input</u>

• In step 1, the post-consumer PET containers are processed into washed and dried flakes. This step is performed by

Decontamination and production of recycled PET material

- In step 2, the flakes are crystallised and decontaminated under high temperature and vacuum.
- In step 3, the decontaminated flakes are extruded to produce pellets.

The operating conditions of the process have been provided to EFSA.

Pellets, the final product of the process, are checked against technical requirements, such as

3.2.2 | Characterisation of the input¹⁰

According to the applicant, the input material for the recycling process Reciclar consists of washed and dried flakes obtained from PET containers, e.g. bottles, previously used for food packaging, from post-consumer collection systems (kerbside and deposit systems). A small fraction may originate from non-food applications. According to the applicant, the proportion will be no more than 5%.

Technical data on the washed and dried flakes are provided, such as on physical properties and residual contents of moisture, poly(vinyl chloride) (PVC), adhesives, other polymers, cellulose and metals (see Appendix A).

3.3 | EREMA Basic technology

3.3.1 Description of the main steps¹¹

The general scheme of the EREMA Basic technology, as provided by the applicant, is reported in Figure 1. The steps are:

- Decontamination in a continuous reactor (step 2):
 The flakes are continuously fed into a reactor equipped with a rotating device, running under high temperature and vacuum for a pre-defined residence time.
 Extrusion of the decontaminated flakes (step 3):
- The flakes, continuously introduced from the previous reactor, are molten in the extruder. Residual solid particles (e.g. or are filtered out of the extruded plastic before the melt is converted to pellets.

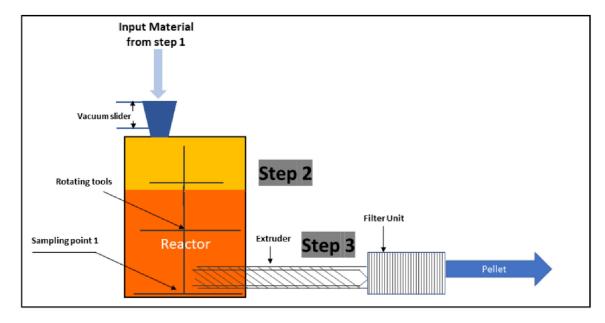


FIGURE 1 General scheme of the EREMA Basic technology (provided by the applicant).

 $^{^{\}rm 10}\text{Technical}$ dossier, section 'Characterisation of the input'.

¹¹Technical dossier, sections 'Recycling process' and 'Determination of the decontamination efficiency of the recycling process'.

The process is run under defined operating parameters ¹² of temperature, pressure and residence time.

3.3.2 Decontamination efficiency of the recycling process¹³

To demonstrate the decontamination efficiency of the recycling process Reciclar, a challenge test on step 2 was submitted to the EFSA.

PET flakes were contaminated with toluene, chlorobenzene, chloroform, methyl salicylate, phenylcyclohexane, benzophenone and methyl stearate, selected as surrogate contaminants in agreement with the EFSA guidelines (EFSA CEF Panel, 2011) and in accordance with the recommendations of the US Food and Drug Administration (FDA, 2006). The surrogates include different molecular masses and polarities to cover possible chemical classes of contaminants of concern and were demonstrated to be suitable to monitor the behaviour of PET during recycling (EFSA, 2008).

Solid surrogates (benzophenone and methyl stearate) were mixed with liquid surrogates (toluene, chlorobenzene, chloroform, methyl salicylate and phenyl cyclohexane) and added to 5 kg of conventionally recycled post-consumer PET flakes. This masterbatch was added to approximately 50 kg PET flakes and stored for 7 days at 50°C with periodical agitation. The contaminated flakes were washed to approximately 50 kg. The contaminated flakes were washed to contaminate flakes were washed the contaminated flakes were washed to contaminate flakes were washed to contaminate flakes were washed the contaminated flakes were washed to contaminate fla



centrations of the surrogates were compared with their initial concentrations in flakes at the inlet of the reactor to derive the decontamination efficiencies (see Table 1).

The decontamination efficiencies presented in Table 1 were calculated for the average residence time in the continuous reactor (step 2) in the challenge test.

¹²In accordance with Art. 9 and 20 of Regulation (EC) No 1935/2004 the parameters were provided to EFSA by the applicant and made available to the Member States and the European Commission (see Appendix C).

 $^{^{13}}$ Technical dossier, section 'Determination of the decontamination efficiency of the recycling process'.

¹⁴Conventional recycling commonly includes sorting, grinding, washing and drying steps and produces washed and dried flakes.

¹⁵'Cross-contamination' (partitioning between green and white flakes), as meant in the Scientific Opinion on 'the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for manufacture of materials and articles in contact with food', is the transfer of surrogate contaminants from the initially contaminated to the initially not contaminated material (EFSA CEF Panel, 2011).

TABLE 1 Efficiency of the decontamination of the continuous reactor (step 2) in the challenge test.

Surrogates	Concentration ^a of surrogates before step 2 (mg/kg PET)	Concentration ^b of surrogates after step 2 (mg/kg PET)	Decontamination efficiency ^c (%)
Toluene	202	0.18	99.1
Chlorobenzene	361	0.36	99.0
Chloroform	291	0.23	99.2
Methyl salicylate	143	0.47	96.6
Phenylcyclohexane	364	1.35	96.2
Benzophenone	480	2.40	94.9
Methyl stearate	360	1.03	97.1

Abbreviation: PET, poly(ethylene terephthalate).

The decontamination efficiency ranged from 94.9% for benzophenone up to 99.2% for chloroform.

3.4 Discussion

Considering the high temperatures used during the process, the possibility of contamination by microorganisms can be discounted. Therefore, this evaluation focuses on the chemical safety of the final product.

Technical data, such as on physical properties and residual contents of PVC, glue, polyolefins and metals, were provided for the input materials (i.e. washed and dried flakes, step 1). The flakes are produced from PET containers, e.g. bottles, previously used for food packaging, collected through post-consumer collection systems. However, a small fraction may originate from non-food applications, such as bottles for soap, mouth wash or kitchen hygiene agents. According to the applicant, the collection system and the process are managed in such a way that this fraction will be no more than 5% in the input stream, as recommended by the EFSA CEF Panel in its 'Scientific Opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for manufacture of materials and articles in contact with food' (EFSA CEF Panel, 2011).

The process is adequately described. The washing and drying of the flakes from the collected PET containers (step 1) is conducted
The EREMA Basic technology comprises the continuous decontamination (step 2) and the extrusion (step 3). The operating parameters of temperature, pressure and residence time for these steps have been provided to EFSA.

A challenge test to measure the decontamination efficiency was conducted on step 2. The reactor was operated under pressure and temperature conditions as well as residence time equivalent to or less severe than those of the commercial process.

The Panel considered that this

challenge test was performed correctly according to the recommendations of the EFSA guidelines (EFSA, 2008) and concluded that step 2 was critical for the decontamination efficiency of the process. Consequently, temperature, pressure and residence time of step 2 should be controlled to guarantee the performance of the decontamination. These parameters have been provided to EFSA (Appendix C).

The decontamination efficiencies obtained from the challenge test on step 2, ranging from 94.9% to 99.2%, have been used to calculate the residual concentrations of potential unknown contaminants in PET ($C_{\rm res}$) according to the evaluation procedure described in the 'Scientific Opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET' (EFSA CEF Panel, 2011; Appendix B). By applying the decontamination percentages to the reference contamination level of 3 mg/kg PET, the $C_{\rm res}$ for the different surrogates was obtained (Table 2).

According to the evaluation principles (EFSA CEF Panel, 2011), the dietary exposure must not exceed 0.0025 μ g/kg bw per day, below which the risk to human health is considered negligible. The $C_{\rm res}$ value should not exceed the modelled concentration in PET ($C_{\rm mod}$) that, after 1 year at 25°C, results in a migration giving rise to a dietary exposure of 0.0025 μ g/kg bw per day. A maximum dietary exposure of 0.0025 μ g/kg bw per day corresponds to a maximum migration of 0.10 μ g/kg of the contaminant into the infant's food and of 0.15 μ g/kg of the contaminant into the toddler's food and has been used to calculate $C_{\rm mod}$ (EFSA CEF Panel, 2011).

The calculated percentages are reported in Table 2. C_{res} reported in Table 2 (scenario for infants) is calculated for 100% recycled PET, for which the risk to human health is demonstrated to be negligible. The relationship between the key parameters for the evaluation scheme is reported in Appendix B.

^aInitial concentration in the contaminated PET flakes.

^bResidual concentration derived for green flakes after decontamination.

^cDecontamination efficiency of step 2 in the challenge test after correction for cross-contamination (see text).

TABLE 2 Decontamination efficiency from the challenge test, residual concentrations of the surrogates (C_{res}) related to the reference contamination level and calculated concentrations of the surrogates in PET (C_{mod}) corresponding to a modelled migration of 0.10 μ g/kg food after 1 year at 25°C.

Surrogates	Decontamination efficiency (%)	C _{res} for 100% rPET (mg/kg PET)	C _{mod} (mg/kg PET); infant scenario
Toluene	99.1	0.03	0.09
Chlorobenzene	99.0	0.03	0.09
Chloroform	99.2	0.02	0.10
Methyl salicylate	96.6	0.10	0.13
Phenylcyclohexane	96.2	0.11	0.14
Benzophenone	94.9	0.15	0.16
Methyl stearate	97.1	0.09	0.32

 $Abbreviations: PET, poly(ethylene\ terephthalate); rPET, recycled\ poly(ethylene\ terephthalate).$

On the basis of the provided data from the challenge test and the applied conservative assumptions, the Panel considered that under the given operating conditions the recycling process Reciclar using the EREMA Basic technology is able to ensure that the level of migration of unknown contaminants from the recycled PET into food is below the conservatively modelled migrations of $0.10\,\mu g/kg$ food. At this level, the risk to human health is considered negligible when the recycled PET is used at up to 100% in mixtures with virgin PET to produce materials and articles intended for contact with all types of foodstuffs, including drinking water bottles (scenario of infants), for long-term storage at room temperature or below, with or without hotfill.

The Panel noted that the input of the process originates from Argentina. In the absence of data on misuse contamination of this input, the Panel used the reference contamination of 3 mg/kg PET (EFSA CEF Panel, 2011) that was derived from experimental data from an EU survey. Accordingly, the recycling process under evaluation using the EREMA Basic technology is able to ensure that the level of unknown contaminants in recycled PET is below a calculated concentration ($C_{\rm mod}$) corresponding to a modelled migration of 0.10 µg/kg food when the recycled PET is used in the proportions described above.

4 | CONCLUSIONS

The Panel considered that the Reciclar recycling process using the EREMA Basic technology is adequately characterised and that the critical step to decontaminate the PET is identified. Having examined the challenge test provided, the Panel concluded that the temperature, the pressure and the residence time in the continuous reactor of step 2 are critical for the decontamination efficiency of the process. Therefore, these are the operating parameters to be controlled.

The Panel concluded that the recycling process Reciclar is able to reduce foreseeable accidental contamination of post-consumer food contact PET to a concentration that does not give rise to concern for a risk to human health if:

- (i) it is operated under conditions that are at least as severe as those applied in the challenge test used to measure the decontamination efficiency of the process;
- (ii) the input material of the process is washed and dried post-consumer PET flakes originating from materials and articles that have been manufactured in accordance with the EU legislation on food contact materials and contain no more than 5% of PET from non-food consumer applications;
- (iii) the recycled PET is used at up to 100% in mixtures with virgin PET for the manufacture of materials and articles intended for contact with all types of foodstuffs, including drinking water bottles, for long-term storage at room temperature, with or without hotfill.

Articles made of this recycled PET are not intended to be used in microwave or conventional ovens and such uses are not covered by this evaluation.

5 | RECOMMENDATION

The Panel recommended periodic verification that the input material to be recycled originates from materials and articles that have been manufactured in accordance with the EU legislation on food contact materials and that the proportion of PET from non-food consumer applications is no more than 5%. This adheres to good manufacturing practice and the Regulation (EC) No 282/2008, Art. 4b. Critical steps in recycling should be monitored and kept under control. In addition, supporting documentation should be available on how it is ensured that the critical steps are operated under conditions at least as severe as those in the challenge test used to measure the decontamination efficiency of the process.

6 | DOCUMENTATION PROVIDED TO EFSA

Dossier 'Reciclar'. November 2022. Submitted on behalf of Reciclar S.A., Argentina. Additional information, June 2023. Submitted on behalf of Reciclar S.A., Argentina. Additional information, October 2023. Submitted on behalf of Reciclar S.A., Argentina.

Additional information, November 2023. Submitted on behalf of Reciclar S.A., Argentina.

ABBREVIATIONS

bw body weight

CEF Panel Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids

CEP Panel Panel on Food Contact Materials, Enzymes and Processing Aids

 $C_{
m mod}$ modelled concentration in PET $C_{
m res}$ residual concentration in PET PET poly(ethylene terephthalate)

PVC poly(vinyl chloride)

rPET recycled poly(ethylene terephthalate)

CONFLICT OF INTEREST

If you wish to access the declaration of interests of any expert contributing to an EFSA scientific assessment, please contact interestmanagement@efsa.europa.eu.

ERRATUM

The opinion was revised due to the availability of more precise data provided by the technology developer, as compared to the information included in Figure 1 (percentage of green flakes in the output of the reactor as a function of time) of the Challenge Test report. The sections affected are the following: Abstract, 3.3.2 Decontamination efficiency of the recycling process, 3.4 Discussion and 4 Conclusions. To avoid confusion, the original version of the output has been removed from the EFSA Journal, and remains available on request.

REQUESTOR

German Competent Authority (Federal Office of Consumer Protection and Food Safety)

QUESTION NUMBER

EFSA-O-2022-00286

COPYRIGHT FOR NON-EFSA CONTENT

EFSA may include images or other content for which it does not hold copyright. In such cases, EFSA indicates the copyright holder and users should seek permission to reproduce the content from the original source.

PANEL MEMBERS

José Manuel Barat Baviera, Claudia Bolognesi, Andrew Chesson, Pier Sandro Cocconcelli, Riccardo Crebelli, David Michael Gott, Konrad Grob, Claude Lambré, Evgenia Lampi, Marcel Mengelers, Alicja Mortensen, Gilles Rivière, Vittorio Silano (until 21 December 2020 †), Inger-Lise Steffensen, Christina Tlustos, Henk Van Loveren, Laurence Vernis and Holger Zorn.

LEGAL NOTICE

Relevant information or parts of this scientific output have been blackened in accordance with the confidentiality requests formulated by the applicant pending a decision thereon by EFSA. The full output has been shared with the European Commission, EU Member States (if applicable) and the applicant. The blackening may be subject to review once the decision on the confidentiality requests is adopted by EFSA and in case it rejects some of the confidentiality requests.

REFERENCES

EFSA (European Food Safety Authority). (2008). Guidelines for the submission of an application for safety evaluation by the EFSA of a recycling process to produce recycled plastics intended to be used for manufacture of materials and articles in contact with food, prior to its authorisation. EFSA Journal, 6(7), 717. https://doi.org/10.2903/j.efsa.2008.717

EFSA (European Food Safety Authority). (2009). Guidance of the Scientific Committee on transparency in the scientific aspects of risk assessments carried out by EFSA. Part2: General principles. EFSA Journal, 7(5), 1051. https://doi.org/10.2903/j.efsa.2009.1051

EFSA (European Food Safety Authority). (2021). Administrative guidance for the preparation of applications on recycling processes to produce recycled plastics intended to be used for manufacture of materials and articles in contact with food. EFSA Journal, 18(3), EN-6512. https://doi.org/10.2903/sp.efsa.2021.EN-6512

EFSA CEF Panel (EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids). (2011). Scientific opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for manufacture of materials and articles in contact with food. EFSA Journal, 9(7), 2184. https://doi.org/10.2903/j.efsa.2011.2184

18314732, 2024. 1, Downloaded from https://efs.aninleibarry.wiley.com/doi/10.2903/jefs.a.024.8518 by Cochrane Argentina, Wiley Online Library on [31/10/2024]. See the Terms and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library on Viley Online Library on Viley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library on Viley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons Licenses and Conditions (https://onlinelibrary.viley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons (https://onlinelibrary.viley.com/terms-and-conditions) on the applicable Creative Commons (https://onlinelibrary.viley.com/terms-and-conditions) on the applicable Creative Commons (

FDA (Food and Drug Administration). (2006). Guidance for industry: Use of recycled plastics in food packaging: Chemistry considerations. https://www.fda.gov/regulatory-information/search-fda-guidance-documents/guidance-industry-use-recycled-plastics-food-packaging-chemistry-considerations

How to cite this article: EFSA CEP Panel (EFSA Panel on Food Contact Materials, Enzymes and Processing Aids), Lambré, C., Barat Baviera, J. M., Bolognesi, C., Chesson, A., Cocconcelli, P. S., Crebelli, R., Gott, D. M., Grob, K., Mengelers, M., Mortensen, A., Rivière, G., Steffensen, I.-L., Tlustos, C., Van Loveren, H., Vernis, L., Zorn, H., Dudler, V., Milana, M. R. . . . Lampi, E. (2024). Safety assessment of the process Reciclar, based on the EREMA Basic technology, used to recycle post-consumer PET into food contact materials. *EFSA Journal*, 22(1), e8518. https://doi.org/10.2903/j.efsa.2024.8518

APPENDIX A

Technical data of the washed flakes as provided by the applicant 16


Parameter	Value
Moisture max	1.5%
Bulk density	320–370 kg/m ³
PVC max	50 mg/kg
Adhesives on flake	< 1000 mg/kg
Other polymers	< 100 mg/kg
Cellulose (paper, wood)	20 mg/kg
Metals	20 mg/kg

Abbreviation: PVC: poly(vinyl chloride).

¹⁶Technical dossier, section Characterisation of the input.

18314732, 2024. 1, Downloaded from https://efs.ao.inlinelibtary.wiley.com/doi/10.2903j.efs.a.2024.8518 by Cochraen Argentina, Wiley Online Library on [31/10/2024]. See the Terms and Conditions (https://onlinelibrary.wiley.com/terms-and-conditions) on Wiley Online Library for rules of use; OA articles are governed by the applicable Creative Commons

Relationship between the key parameters for the evaluation scheme (EFSA CEF Panel, 2011).

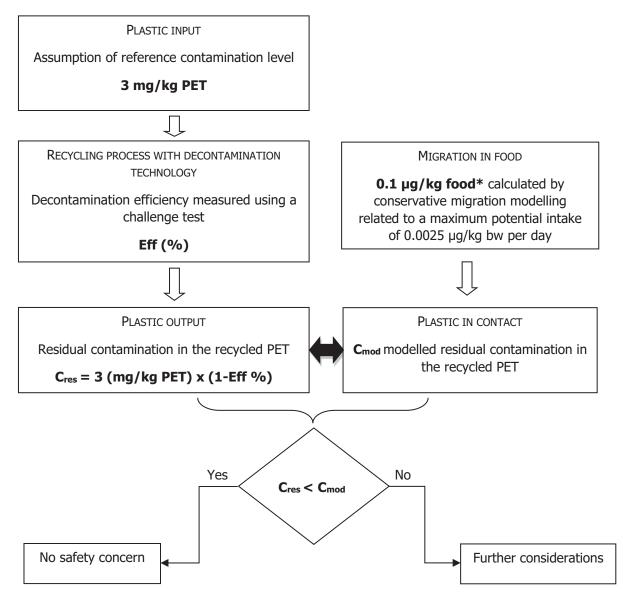

^{*}Default scenario (infant). For adults and toddlers, the migration criterion will be 0.75 and 0.15 µg/kg food, respectively. The figures are derived from the application of the human exposure threshold value of 0.0025 µg/kg bw per day applying a factor of 5 related to the overestimation of modelling.

APPENDIX C





¹⁷Technical dossier, section 'Table of operating parameters'.



